

ISSN 0866-708X

VIỆN HÀN LÂM KHOA HỌC VÀ CÔNG NGHỆ VIỆT NAM
VIETNAM ACADEMY OF SCIENCE AND TECHNOLOGY

TẠP CHÍ

KHOA HỌC VÀ CÔNG NGHỆ

JOURNAL OF SCIENCE AND TECHNOLOGY

Tập 55 - Số 1B
2017



International Symposium on
MATERIALS SCIENCE and ENGINEERING 2017

March 13-15, 2017 - Ho Chi Minh City, Vietnam

ENZYMATIC PREPARATION OF MODULATED-BIODEGRADABLE HYDROGEL NANOCOMPOSITES BASED CHITOSAN/GELATIN AND BIPHASIC CALCIUM PHOSPHATE NANOPARTICLES

Nguyen Tien Thinh¹, Nguyen Thi Phuong², Bui Thanh Thai²,
Nguyen Trong Tri³, Nguyen Huynh Bach Son Long³, Tran Quoc Son³,
Nguyen Tri Phu², Nguyen Cuu Khoa², Nguyen Dai Hai², Tran Ngoc Quyen^{1,2,*}

¹School of Medicine and Pharmacy, Tra Vinh University
126 National Road 53, Ward 5, Tra Vinh City, Tra Vinh Province, Vietnam

²Institute of Applied Materials Science, VAST
1 Mac Dinh Chi Street, Ben Nghe Ward, District 1, Ho Chi Minh City, Vietnam

³Department of Chemical Engineering, Lac Hong University
10 Huynh Van Nghe Street, Buu Long Ward, Bien Hoa City, Dong Nai Province, Vietnam

*Email: tnquyen979@gmail.com

Received: 30 December 2016; Accepted for publication: 6 March 2017

ABSTRACT

In the study, injectable chitosan–4 hydroxyphenylacetamide acid (CHPA) and gelatin–tyramine (GTA)–based hydrogels were enzymatically prepared, in which could encapsulate biphasic calcium phosphate nanoparticles (BCP NPs) for enhancing bone regeneration. The *in situ* formation of hydrogel composite was varied from 35 to 80 seconds depending on concentration of H₂O₂. Collagenase–mediated biodegradation of the hydrogel composite could be modulated from 3 days to over one month depending on amount of the formulated CHPA. Live/dead cell viability assay indicated that the hydrogel composite enhanced bone marrow mesenchymal stem cells (MSCs). The obtained results show a great potential of the hydrogel composites for bone regeneration due to its adjustable biodegradation, biocompatibility and enhancement in new bone formation.

Keywords: chitosan, gelatin, horseradish peroxidase (HRP), hydrogel, collagenase.

1. INTRODUCTION

Recently, biological hydrogels have played an important role in the advanced biomaterials for tissue regeneration and drug delivery systems. Several kinds of the injectable hydrogels performed an effective encapsulation of drugs/cells and convenience for applying the minimally invasive implant surgery [1]. The hydrogels play a role as an artificial extracellular matrix (ECM) and proliferation allowing transportation of nutrients

2.2.2. Preparation of tyramine conjugated gelatin (GTA)

Gelatin skin (2g) and TA (1.00 g, 7.3 mmol) were dissolved in DI water (30 mL). The pH of the mixture was adjusted to 6 following addition of EDC (0.50 g, 2.5 mmol) under stirring for 24 h. Then, the solution was dialyzed against deionized water using membrane dialysis (MWCO6000–8000) for 3 days. Subsequently, the dialyzed solution was lyophilized to obtain GTA as shown in Figure 2. Theyield was 1.80 g. ¹H NMR (D₂O)/ppm: δ 6.75 and 7.11 (d, -CH=CH- of TA), δ 2.65 and 2.88 (m, -CH₂CH₂-, TA).

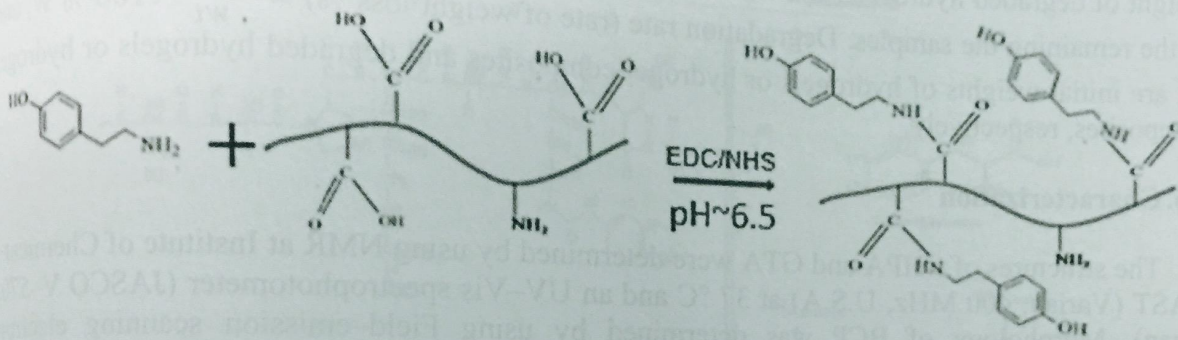


Figure 2. Synthetic scheme of GTA.

2.2.3. Preparation of BCP

BCP were synthesized using an ultrasonic assisted process. The calcium chloride reacted to tricalcium phosphate salts with molar ratio of Ca/P = 1.57 for 12 h at 50 °C under controlled pH 7 to obtain a white suspension. The pH solution was maintained by adding of sodium hydroxide solution. The precipitate was washed with DI water and dried in an oven at 70 °C. Finally, the calcination was carried out at 750 °C.

2.3. Preparation of gelatin and chitosan-based hydrogels

GTA (40 mg) was dissolved in DI water (300 μL) and separated into two vials equally. Then, enzyme HRP (30 μL of 0.07 mg/mL) and H₂O₂ (30 μL of 0.03–0.07 wt/vol%) were added into each tube. GTA hydrogel was formed by mixing the solution of 10 wt/wt% polymer. CHPA hydrogel was prepared by a same above process. HRP (30 μL of 0.05 mg/mL) and H₂O₂ (30 μL of 0.05–0.2 wt/vol%) were added into each tube. The final concentration of the polymer solution was 2 wt/wt%. The gelation time was determined by using the vial tilting method.

2.4. Preparation of chitosan/gelatin-based hydrogels, hydrogel composites

Precursor polymer solutions were prepared in four vials. In each vial A and B, GTA (20 mg) were dissolved completely in DI water (150 μL). In vial C and D, CHPA (10 mg) dissolved in DI water (160 μL). 30 μl HRP (0.07 mg/mL) was added into A, C and 30 μL H₂O₂ (0.05–0.2 wt/vol%) was added into B, D. A was mixed with C, B was mix with D. Finally, two polymer solutions containing HRP and H₂O₂ were interfused together to create *in situ* formation GTA or CHPA hydrogels at 8 wt/wt% of the polymer concentration. The hydrogel composites containing BCP nanoparticles (10 wt/wt%) was prepared by the same manner. The gelation time of the samples were studied based on variation of the concentration of H₂O₂ from 0.05, 0.07, 0.1, 0.2 wt/vol%.

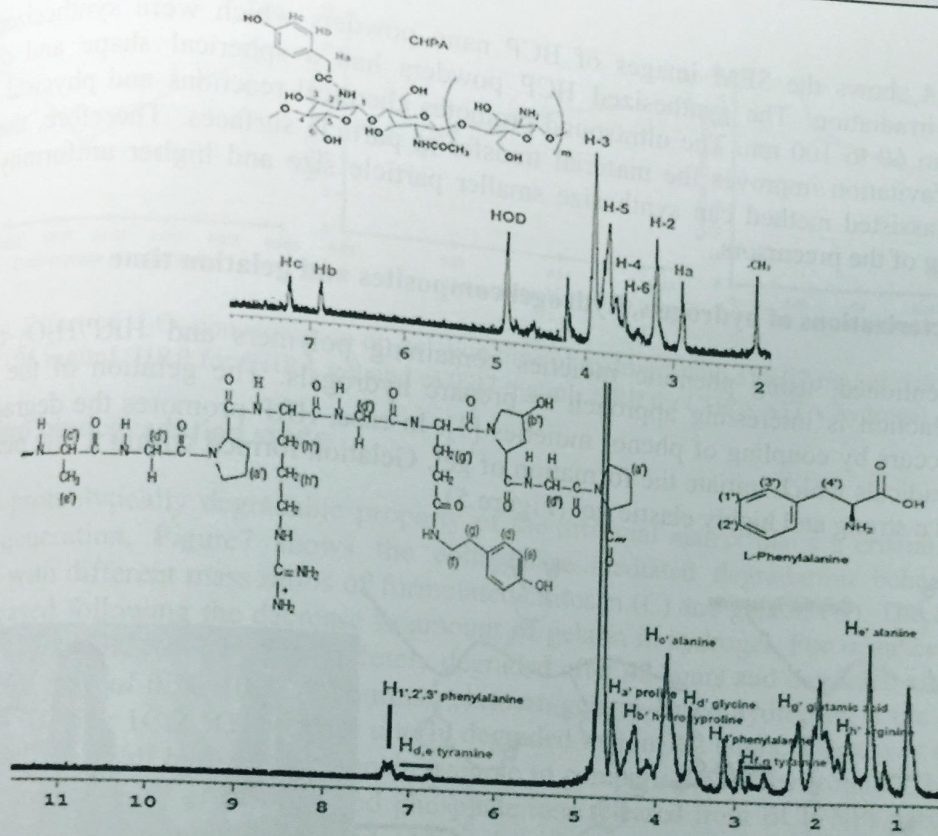


Figure 3. ¹H NMR spectrum of chitosan 4-hydroxyphenylacetic acid (CHPA, top) and gelatin-tyramine (GTA, bottom) in D₂O.

3.2. Characterizations of BCP

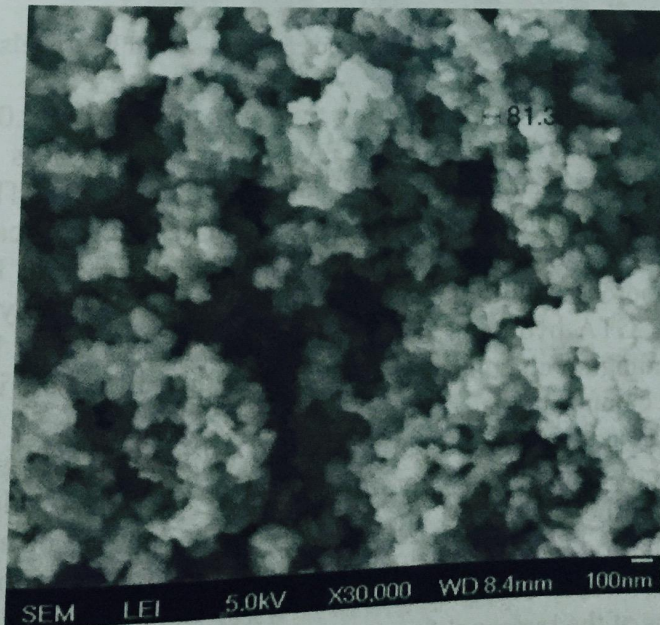


Figure 4. SEM image of the BCP nanoparticles.

Figure 4 shows the SEM images of BCP nano powders which were synthesized using ultrasound irradiation. The synthesized BCP powders had a spherical shape and diameter ranging from 60 to 100 nm. The ultrasound promotes chemical reactions and physical effects; therefore, use of the ultrasonic cavitation improves the material transfer at particle surfaces. Therefore, use of the ultrasound-assisted method can synthesize smaller particle size and higher uniformity due to good mixing of the precursors.

3.3. Characterizations of hydrogels, hydrogel composites and gelation time

As mentioned, using phenolic moieties containing polymers and HRP/H₂O₂-mediated coupling reaction is interesting approach to prepare hydrogels. The gelation of the polymer solutions occurs by coupling of phenol moieties [3]. In case, HRP promotes the degradation of H₂O₂ into radicals which initiate the formation of gel. Gelation formed within a few period time and formed a strong and highly elastic gel (Figure 5).

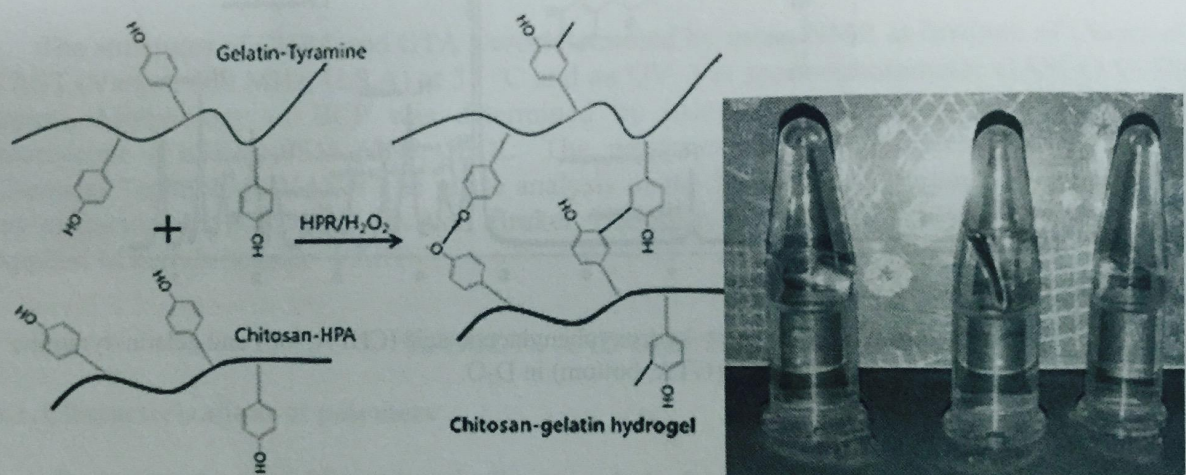


Figure 5. Formation of gelatin and chitosan-based hydrogels.

Figure 6a, indicate that the lowest gelation time was obtained at 0.07 wt% concentration of H₂O₂ and HRP (0.05 mg/mL) in 12 s for CHPA hydrogel and in 50 s for GTA hydrogel at 0.05 wt% concentration of H₂O₂ and 0.07 mg/mL concentration of HRP. This could result in the numbers of phenolic groups coupled to GTA were less than to CHPA. In cases of CHPA gel and GTA gel, an increment of H₂O₂ concentration at the fixed HRP could lead to extending the gelation time because more phenolic radicals were produced in their polymer solutions. Figure 6c indicated that CHPA-GTA hydrogels and hydrogel composites could be formed below one and half minutes depending on amount of H₂O₂. It is a lightly difference in gelation time of the hydrogel and hydrogel composite that contributes from presence of BCP NPs. Functional NH₂, OH, COOH groups of gelatin and amine groups chitosan link with OH groups of HAP in BCP composites decreased. In the study, it is important to use an amount of hydrogen peroxide in a cell-favorable range that doesn't induce cell apoptosis. So molar ratio of H₂O₂ and phenol groups should be matched each other. In the fact, concentration of H₂O₂ could be significantly decreased in the process of the hydrogel formation due to oxidation of phenol moieties.

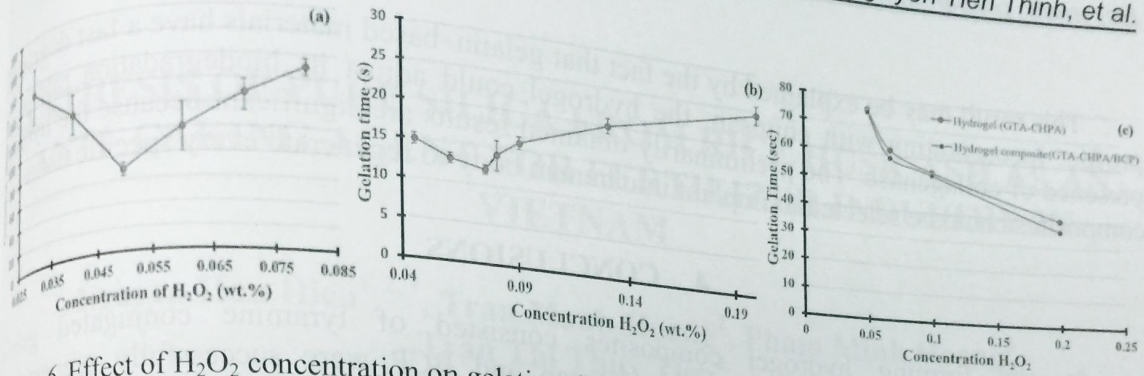


Figure 6. Effect of H₂O₂ concentration on gelation time of hydrogel with a) 0.07 mg/mL HRP for GTA gel, b) 0.05 mg/mL HRP for CHPA gel and c) 0.07 mg/mL HRP for CHPA-GTA hydrogel composite.

3.4. *In vitro* biodegradation study

The proteolytically degradable property of the artificial matrix plays a crucial role in the tissue regeneration. Figure 7 shows the collagenase-mediated degradation behavior of the materials with different mass ratios of formulated chitosan (C) and gelatin (G). The degradation rate decreased following the decrease in amount of gelatin in hydrogel. For instance, hydrogels at a mass ratio of 0C:10G were completely degraded after 42 hours and degraded after 90 hours for the mass ratio of 0.5C:10G. In contrast, chitosan/gelatin-based hydrogels at the mass ratios of 1C:10G; 1C:5G; 1C:2.5G were not utterly degraded within 768 hours. There was a prolonged degradation rate of all hydrogel composite sample in comparison with hydrogels. This could be explained that presence of calcium and phosphate ions released from BCP NPs participating to cross-linking reaction with amine and carboxylate groups in polymers resulting in increasing cross-linking density.

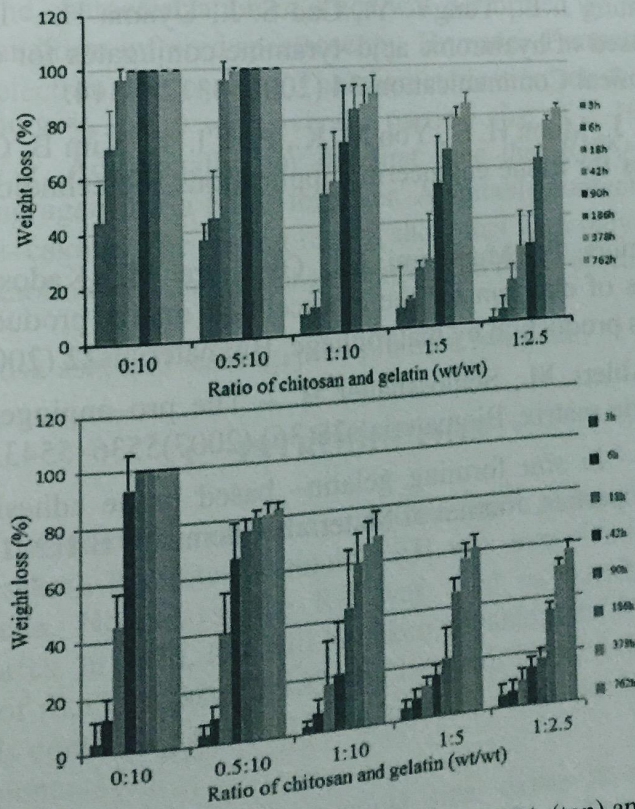


Figure 7b. *In vitro* biodegradation rate of hydrogels GTA-CHPA (top) and hydrogel composite GTA-CHPA (bottom) in presence of collagenase enzyme.

This result may be explained by the fact that gelatin-based materials have a fast degradable profile. Incorporating with chitosan, the hydrogel could adjust its biodegradation rate in the presence of collagenase. The preliminarily obtained results are significant because the hydrogel composites could be selected to implant into human body to regenerate every specific tissue.

4. CONCLUSIONS

In situ forming hydrogel composites consisted of tyramine conjugated gelatin, 4-hydroxyphenylacetic acid conjugated chitosan and BCP were successfully prepared via horseradish peroxidase mediated reaction in the presence of hydrogen peroxide. With a rapid gelation time at the physiological condition and controllable biodegradation rate, the hydrogel composites will be significant to apply in regenerative medicine.

Acknowledgements. This work was financially supported by Vietnam National Foundation for Science and Technology Development (NAFOSTED) [grant number 106-YS.99-2014.33].

REFERENCES

1. Schmaljohann D. – Thermo- and pH-responsive polymers in drug delivery, *Advanced Drug Delivery Reviews* **58** (15) (2016) 1655–1670.
2. John A., Sharon K., Luke M., Declan M. D., Eoin S., Daniel B., Clement L. H. – Hydrogel/bioactive glass composites for bone regeneration applications: synthesis and characterization, *Materials Science and Engineering C* **33** (2013) 4203–4212.
3. Kurisawa M., Chung J. E., Yang Y., Gao S. J., Uyama H. – Injectable biodegradable hydrogels composed of hyaluronic acid-tyramine conjugates for drug delivery and tissue engineering, *Chemical Communications* **34** (2005) 4312–4314.
4. Kim I. Y., Seo S. J., Moon H. S., Yoo M. K., Park I. Y., Kim B. C., Cho C. S. – Chitosan and its derivatives for tissue engineering applications, *Biotechnology Advances* **26** (2008) 1–21.
5. Ueno H., Nakamura F., Murakami M., Okumura M., Kadosawa T., Fujinaga T. – Evaluation effects of chitosan for the extracellular matrix production by fibroblasts and the growth factors production by macrophage, *Biomaterials* **22** (2001) 2125–2130.
6. Dreesmann L., Ahlers M., Schlosshauer B. – The pro-angiogenic characteristics of a cross-linked gelatin matrix, *Biomaterials* **28**(36) (2007) 5536–5543.
7. Yunki L., et al. – *In situ* forming gelatin-based tissue adhesives and their phenolic content-driven properties, *Journal of Materials Chemistry B* **1**(2013) 2407–2414.